



# Evaluation of the Physical and Thermal Properties of Fibers Extracted from the Trunks of *Urena Lobata* and *SIDA Stipulata* Plants

**Alphousseyni Ghabo <sup>a\*</sup>, Seckou Bodian <sup>b</sup>  
and El hadji Dieng <sup>b</sup>**

<sup>a</sup> *Laboratoire des Semi-Conducteurs et d'Energie Solaire, Faculté des Sciences et Techniques, Université Cheikh Anta, Diop de Dakar, Dakar, Sénégal.*

<sup>b</sup> *Laboratoire Eau, Energie, Environnement et Procédés Industriels, Ecole Supérieure Polytechnique, Dakar, Sénégal.*

## **Authors' contributions**

*This work was carried out in collaboration among all authors. All authors read and approved the final manuscript.*

## **Article Information**

DOI: 10.9734/CJAST/2024/v43i44371

## **Open Peer Review History:**

This journal follows the Advanced Open Peer Review policy. Identity of the Reviewers, Editor(s) and additional Reviewers, peer review comments, different versions of the manuscript, comments of the editors, etc are available here: <https://www.sdiarticle5.com/review-history/114789>

**Original Research Article**

**Received: 24/02/2024**  
**Accepted: 27/03/2024**  
**Published: 10/04/2024**

## **ABSTRACT**

This scientific work was carried out to investigate the properties (hygroscopic, physical and thermal) of fibers extracted from the *Urena Lobata* and *Sida Stipulata* plants, in order to compare them with other fibers already used in the manufacture of panels or biosourced concretes. The fibers are manually detached from the plant trunk, then dried and studied. The results of the study revealed that *Urena Lobata* fibers are more sensitive to water. The water absorption rate and water content were respectively evaluated at 228.58% and 10.5% for *Urena Lobata* fibers and 220.94% and 8.6% for *Sida Stipulata* fibers. For densities ranging from 111 to 193.31 kg/m<sup>3</sup>, the measured thermal

\*Corresponding author: E-mail: [alphousseynighabo@gmail.com](mailto:alphousseynighabo@gmail.com);

conductivities are between 0.046 - 0.075 W/ mK for Urena Lobata fibers and 0.043 - 0.064 W/mK for Sida Stipulata fibers. These results show that both types of fiber can be used in the manufacture of thermal insulation materials.

*Keywords: Urena Lobata fibers; Sida Stipulata fibers; density; water absorption; thermal conductivity.*

## 1. INTRODUCTION

The global energy consumption and carbon dioxide emissions in the building sector are estimated at 34% and 37% in 2021 [1]. This is due to the fact that the building envelope is essentially made of cement bricks, which are materials capable of storing large quantities of energy and releasing it in the form of heat. In order to ensure thermal comfort in these homes, building occupants use ventilation and air-conditioning systems that increase energy consumption. The manufacture of cement and the use of concrete in building construction therefore have a major impact on energy consumption and carbon dioxide emissions. According to Marinković et al. [2], global concrete production is estimated at 6 billion tonnes per year. For this reason, the production of new types of concrete (bio-sourced concretes) with good thermal performance and low environmental impact would be a relevant solution for reducing energy consumption in the building sector. As a result, a considerable number of scientific studies have focused on the use of plant fibers as reinforcing materials in concrete.

The advantage of using plant fibers in concrete reinforcement is that they are locally available, lightweight, biodegradable and offer excellent thermal and acoustic insulation properties [3]. Several characterization studies have been carried out in the literature to assess the chemical, hygroscopic, physical and thermal properties of plant fibers. Some researchers have focused on chemical composition, determining the organic constituents of fibers such as cellulose, hemicellulose and lignin [4,5]. Khiari et al. [6] carried out a study on Posidonia-Oceanica fibers, showing that they contain 61.8% cellulose (cellulose and hemicellulose) and 29.8% lignin. The same work was carried out by Mbouyap et al. [7] on Banana fibers. Their results showed the presence of 58.3% cellulose, 12% hemicellulose, 10% lignin and 29.7% extractables. Other researchers have evaluated the hygroscopic and thermo-physical properties, such as water absorption, density and thermal conductivity, of certain plant fibers. Libog et al.

[8] determined the properties of fibers extracted from banana trunks. Their study showed that it has a water absorption rate between (347.1-517.4%) and a density of (0.9-1.45 g/cm<sup>3</sup>). The study of typha fibers by Diaw et al. [9] reveals high water absorption and low density (56.44 kg/m<sup>3</sup>). To assess the thermal insulation potential of date palm fibers, Ali et al. [10] measured thermal conductivity for different densities. The results revealed that for densities of (176 kg/m<sup>3</sup>-260 kg/m<sup>3</sup>), the fibers exhibit low thermal conductivities (0.0475- 0.0697 W/mK). A similar study was carried out on Posidonia-Oceanica fibers by Hamdaoui et al. [11]. The authors varied the density from 17 kg/m<sup>3</sup> to 155 kg/m<sup>3</sup> and found that the thermal conductivity values of the fibers ranged from 0.046 to 0.070 W/mK. Wei et al. [12] investigated a rice husk insulating material. For densities of 200 kg/m<sup>3</sup> to 350 kg/m<sup>3</sup>, the corresponding thermal conductivities are 0.051 W/mK to 0.053 W/mK. Several other types of fiber have been studied, such as flax fibers [13], jute fibers [14], flax fibers [15], pineapple leaf fibers [16], baobab trunk fibers [17], Diss and Doum fibers [18]. From the results of these different studies, we can see that these plant fibers have variable hygroscopic and thermo-physical properties. This dispersion of fibers properties can be linked to development zones and conditions, structure (porosity) and chemical composition (lignin, cellulose, hemicellulose etc.), extraction zone (stem, trunk, leaves, nuts etc.) [19,20].

However, no studies on the physical and thermal characterization of Urena Lobata and Sida Stipulata plant fibers have been found in the literature. This article proposes the characterization of these two types of fibers in order to use them as reinforcement material in concrete or to produce thermal insulation boards. Urena Lobata L. and Sida Stipulata L. are both wild plants in the Malvaceae family. With cylindrical trunks and essentially fibrous bark, these plants can reach heights of 1.5 m to 2 m. They grow during the rainy season in the south and southeast of Senegal. The long fibers extracted from the trunk of the Urena Lobata plant have been used for a long time by our ancestors to make ropes and weave mats. In this

article, we focus on evaluating the physical properties (water absorption, density) and thermal conductivity of the fibers.

## 2. MATERIALS AND METHODS

### 2.1 Plant Fibers

The studied fibers were extracted from Urena Lobata L. and Sida Stipulata L. plants collected in the village of Koling / Sédhiou region / Senegal (Fig.1). The fibers were extracted manually, as the bark detaches easily from the stem. After extraction, the fibers were air-dried for 2 weeks.

### 2.2 Water Absorption Rate

The water absorption rate of the fibers was determined by the distilled water immersion method. The fibers were first dried in an oven at 105°C for 24 h, then weighed. Placed in a tube pierced with small holes, the fiber-tube assembly was introduced into water at an average temperature of 27°C. Every 30 min, the fibers were removed from the water and lightly shaken to remove water from the surfaces, then weighed using a 0.01g precision balance. Weighing operations are repeated until the fiber mass has become constant. The water absorption rate is calculated by Eq. 1 [7,8,21].

$$W_{abs} = \frac{m_h - m_i}{m_i} \times 100 \quad (1)$$

$m_h$  : mass of humid fibers,  $m_i$  : initial fibers mass

### 2.3 Water Content

The moisture content of the fibers is determined by the oven-drying method. A sample of each type of fiber is weighed with a 0.01 g precision balance, then dried in an oven at 105°C for 48 hours. Fiber water content is calculated using Eq. 2:

$$M_c = \frac{m_s - m_i}{m_i} \times 100 \quad (2)$$

$m_s$ : Dry fiber mass

### 2.4 The Bulk Density

The density of a material is the ratio of its mass to its apparent volume. To evaluate density, the apparent volume (V) of the fibers is determined using a cylindrical mold, then their corresponding mass (m) is measured using a 0.01 g precision balance. The mass is calculated by the Eq 3:

$$\rho = \frac{m}{V} \quad (3)$$

### 2.5 Thermal Conductivity

Thermal conductivity was assessed using the thermal box method. A Plexiglas dial with dimensions of 27cm x 27cm x 5 cm was used to contain the raw fibers (Fig. 2). By increasing the compaction pressure of the fibers in the same dial, three densities were used to measure the thermal conductivities of the fibers.



Fig. 1. a- Urena lobata plant, b- Urena lobata fibers, c- Sida Stipulata plant, d- Sida Stipulata fibers



**Fig. 2. Fibers sample**


The principle of this method is to send a constant flow of heat ( $\Phi$ ) to one side of the sample using a heating resistance (Fig.3). With thermocouples attached to both sides of the sample, temperatures are measured when steady state is established. To minimize heat loss (C) through the box faces, the voltage is set so that the temperature in the box is slightly higher than the ambient temperature ( $(T_b - T_a) < 1^\circ\text{C}$ ). The heat transfer in the box is given by Eq. 4:

$$\varphi = \varphi_u + \varphi_p \quad (4)$$

With:  $\varphi = \frac{U^2}{R}$ , the heat flux from the heating element

$\varphi_u = \frac{\lambda S}{e}(T_c - T_f)$ : the heat flux that passes through the sample

$\varphi_p = C(T_B - T_a)$ : the lost heat flux

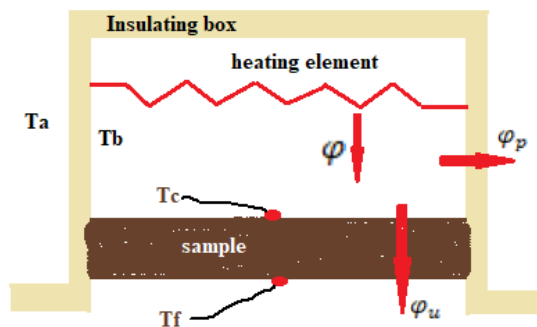

**Fig. 3. Sample in thermal box**

Replacing these expressions in Eq. 4, we derive the expression for the thermal conductivity of the sample by Eq. 4:

$$\lambda = \frac{e}{S(T_c - T_f)} \left[ \frac{U^2}{R} - C(T_B - T_a) \right] \quad (5)$$

U: The voltage

R: Heating element thermal resistance

T<sub>c</sub>: Heating face temperature

T<sub>B</sub>: Box temperature

T<sub>f</sub>: Cooling face temperature

T<sub>a</sub>: Ambient temperature

### 3. RESULTS AND DISCUSSION

#### 3.1 Water Absorption

The water absorption rate of fibers is an important parameter in determining the maximum amount of water that can be absorbed, and the maximum immersion time to reach water saturation. During the manufacture of bio-composite concrete, this quantity of water must be taken into account when assessing the optimum mixing ratio (water/binder) to ensure proper binder adhesion. Fig. 4 shows the evolution of water absorption rate as a function of fiber immersion time. It can be seen from Fig. 4 that during the first four hours of immersion, the fibers absorb water more rapidly. After four hours, their capacity to absorb water begins to diminish, reaching saturation after 14 hours of immersion. This is because plant fibers are cellulosic materials whose hydrophilic character is due to the fact that their structure is made up of many capillary pores. In addition, their structure contains a large number of hydroxyl groups linked to the presence of lignin and hemicelluloses, which are capable of binding large quantities of water molecules [16,21,22]. In this study, maximum water absorption rates were 228.58% for Urena Lobata L. fibers and 220.94% for Sida Stipulata L. fibers. Similar studies on plant fibers (Table 1), investigating the water absorption of different fibers, show that the water absorption values of Urena Lobata and Sida Stipulata fibers are within the range of those of plant fibers found in the literature.

#### 3.2 Water Content

Determining the water content provides information on the hygroscopic state of the fibers under ambient conditions. The water contents of the two types of fiber are shown in Table 2. The traces of water in the internal structure of fibers can be explained by the presence of hydroxyl groups in lignin and hemicellulose, the non-cellulose components of fibers. Through Van Der Waal-type hydrogen bonds, these components are able to bind water molecules in vapour form and, through the process of vapour diffusion and capillary condensation, water is formed in the fibers pores [25]. Table 2 shows that the water content of Urena Lobata fibers (10.5%) is higher than that of Sida Stipulata fibers (8.6%) under

ambient conditions. This may be due to the fact that there are more hydroxide groups in Urena Lobata fibers. Table 2 shows the water content values of various plant fibers. It can be seen that the water contents of the fibers studied are in the same range as those of many fibers found in the literature.

### 3.3 The Bulk Density


The bulk densities of both types of fibers were measured and their values are shown in Table 2. In general, plant fibers have lower bulk densities than conventional fibers. The low density of plant fibers can be attributed to the high internal porosity of their structures, which results in the

high water absorption of plant fibers [9]. This is due to the presence of amorphous components such as lignin and hemicelluloses, whose structure contains large quantities of voids. Table 2 shows that Urena Lobata fibers have a higher density than Sida Stipulata fibers. This result can be justified by the fact that Urena Lobata fibers have less pores. In addition, the fibers studied have lower densities than date palm [10] and Diss or Doum [18] fibers. However, typha plant fibers are much lighter than the fibers studied. This dispersion of plant fiber density values is linked to several parameters: extraction position on the plant, development zone, chemical composition, etc.

**Table 1. Water absorption rates of some fibres**

Types of fibers	Water absorption (%)	Immersion times	Autors
Ananas Comosus fibers	268	24 h	[16]
Banana Fibers	347.1- 517.4	48 h	[8]
Raffia vinifera fibers	303-662	24 days	[23]
Hemp fibers	62	13 h	[24]
Urena Lobata fibers	228.58	14 h	PW
Sida Stipulata fibers	220.94	14 h	PW

PW: Present Work

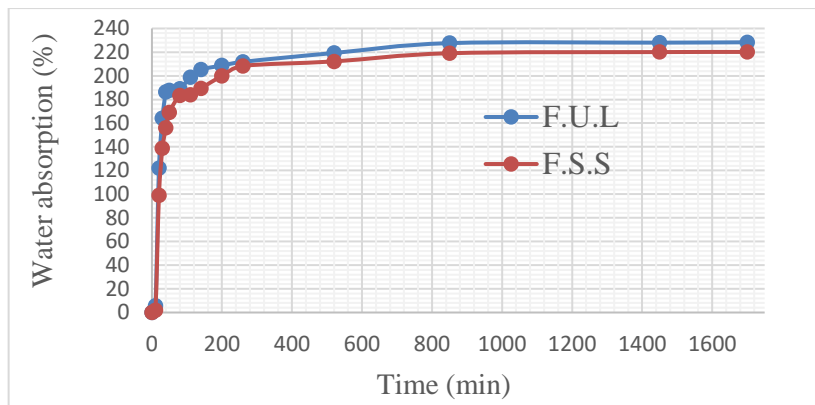

**Fig. 4. Water absorption of fibers**

**Table 2. Water content of various fibers**

Type of fibers	Urena Lobata	Sida Stipulata	Banana	Typha plant	Carnauba	Ficus Carica	Hibiscus Vitifolius	Bambou
Water Content	10.5	8.6	10.6-12.4	1.4	7.2	9.07	11.31	9.16
Autors	PW	PW	[7]	[9]	[5]	[4]	[26]	[27]

**Table 3. Densities of different fibers**

Type of fibers	Urena Lobata	Sida Stipulata	Palmier dattier	Diss and Doum	Typha plant
Density (kg/m <sup>3</sup> )	239.63	201.14	176-210	850 and 447	56.44
Autors	PW	PW	[10]	[18]	[9]



### 3.4 Thermal Conductivity

In order to assess the thermal insulation potential of the fibers, their thermal conductivities were measured using the thermal box method. The conductivity values measured for both types of fiber are shown in Table 4. The evolution of thermal conductivity as a function of density for each fiber type is shown in Fig. 5.

Initially, Fig. 5 shows that the thermal conductivity of the fibers increases as the density of the fibers increases; this is observed for both types of fiber. Indeed, an increase in density leads to a decrease in the porosity of a sample. However, in order to increase the density, it was necessary to increase the quantity of fibers in the same dial, which also means increasing the compaction pressure to fill the dial. The porosity of the sample decreases with increasing fiber quantity in the same dial. This justifies the fact that thermal conductivity increases as density increases. Similar studies on rice husk and Posidonia-Oceanica fibers, by Wei et al. [12] and Hamdaoui et al. [11] respectively, have

also shown that the thermal conductivity of fibers varies in the same direction as density.

Secondly, it can be seen from Fig. 5 that Stipulata sida fibers showed better thermal conductivity values than Urena Lobata fibers. In fact, even though they are both of plant origin, these fibers do not have the same internal structure, which is an important parameter in terms of a fiber's properties. As shown in Table 3, the density of Urena Lobata fibers is higher than that of Sida Stipulata fibers. For this reason, Urena Lobata fibers are less porous and therefore more heat-conductive. This is why the superior thermal conductivity of Urena Lobata fibers was observed.

Table 4 illustrates the thermal conductivity values of the fibers studied and those of some fibers found in the literature. As can be seen, the fibers studied (Urena and sida) presented low thermal conductivities that are very close to those of other fiber types already studied for use as thermal insulation materials.

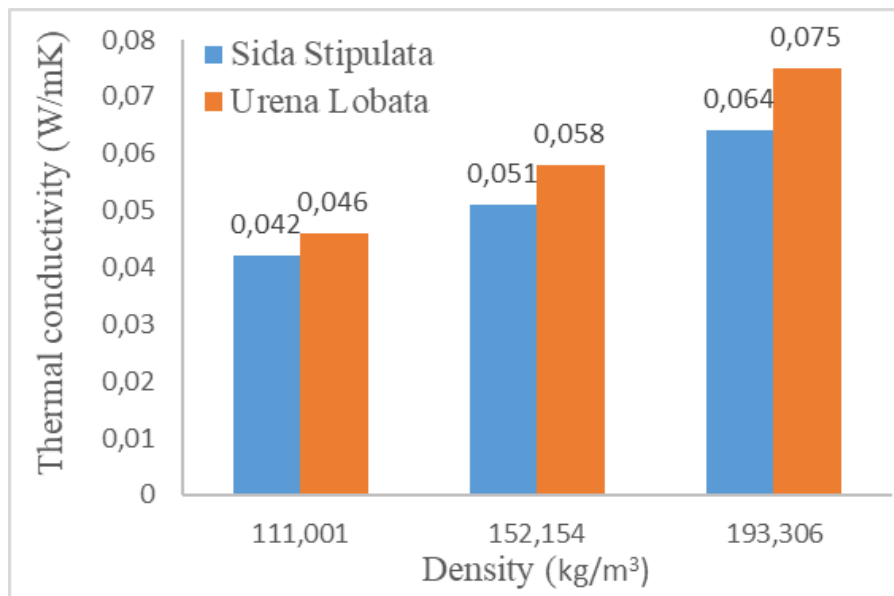


Fig. 5. Thermal conductivity as a function of density

Table 4. Thermal conductivity of different types of fibers

Type of fibers	Urena Lobata	Sida Stipulata	Race Straw	Posidonia Oceanica	Date palm surface fibers
Thermal conductivity (W/mK)	0.046-0.075	0.043-0.064	0.051-0.053	0.043-0.070	0.0475-0.0697
Auteurs	PW	PW	[12]	[11]	[10]

#### 4. CONCLUSION

The development of composite materials using plant fibers requires a thorough understanding of their properties. For this reason, Urena Lobata and sida Stipulata fibers have been characterized. The study consisted in determining the water absorption, density and thermal conductivity of the fibers. The results showed that both types of fiber have a higher water absorption capacity than conventional fibers. However, both types of fiber are lightweight and have low thermal conductivities. A simple comparison shows that these fibers have properties similar to those found in the literature. They can therefore be used in the manufacture of biosourced panels and concretes.

#### COMPETING INTERESTS

Authors have declared that no competing interests exist.

#### REFERENCES

- Available: <https://globalabc.org/our-work/tracking-progress-global-status-report>
- Marinković S, Radonjanin V, Malešev M, Ignjatović I. Comparative environmental assessment of natural and recycled aggregate concrete. *Waste Management*, 2010;30(11):2255–2264. Available: <https://doi.org/10.1016/j.wasman.2010.04.012>
- Lee CH, Khalina A, Lee SH. Importance of interfacial adhesion condition on characterization of plant-fiber-reinforced polymer composites: A review. *Polymers*, 2021;13(3):438. Available: <https://doi.org/10.3390/polym13030438>.
- Manivel Selvaraj, Pannirselvam N, Ravichandran P T, Bhuvaneshwaran Mysamy, Samson S Extraction and Characterization of a New Natural Cellulosic Fiber from Bark of *Ficus Carica* Plant as Potential Reinforcement for Polymer Composites, *Journal of Natural Fibers*. 2023;20(2):2194699. Available: <https://doi.org/10.1080/15440478.2023.2194699>.
- Rai Felipe Pereira Junio, Lucas de Mendonças Neuba, Andressa Teixeira Souza, Artur Camposo Pereira, Lucio Fabio Cassiano Nascimento, Sergio Neves Monteiro Thermochemical and structural characterization of promising Carnauba novel leaf fibers (*Copernicia prunifera*). *J. Mater. Res. Technol.* 2022;18:4714-4723. Available: <https://doi.org/10.1016/j.jmrt.2022.04.127>
- Khiari MF, Mhenni MN, Belgacem E, Mauret, Chemical composition and pulping of date palm rachis and *Posidonia oceanica*, *Bioresour. Technol.* 2010;101:775–780. Available: <https://doi.org/10.1016/j.biortech.2009.08.079>
- Anatole Chengoue Mbouyap, Théodore Tchotang, Christian Fokam Bopda, Herman Lekane Assonfack, Jean Bosco Saha Tchinda, Maxime Arnaud Cheumani Yona. Impact of Cultivation Area on the Physical, Chemical, and Mechanical Properties of Banana Pseudo-Stems Fibers in Cameroon, *Journal of Natural Fibers*. 2023;20(2):2198274. Available: <https://doi.org/10.1080/15440478.2023.2198274>
- Laurent Libog, Florent Biyeme, Achille Désiré Omgba Betené, Achille Bernard Biwolé, Benoit Ndiwe, Jonas Peequeur Essome Mbang, Takoumbe Claude, Jean Aimé Mbey, and Jean Raymond Lucien Meva'a, Influence of the Extraction Location on the Physical and Mechanical Properties of the Pseudo-Trunk Banana Fibers, *Journal of Natural Fibers* 2023;20. Available: <https://doi.org/10.1080/15440478.2023.2204451>
- Ibrahima Diaw, Mactar Faye, Seckou Bodian and Vincent Sambou, Effects of chemical treatment on the physical properties of Typha, *Fluid dynamics and materials processing*. 2022;18. Available: <https://doi.org/10.32604/fdmp.2022.021968>
- Mohamed E. Ali, Abdullah Alabdulkarem, on thermal characteristics and microstructure of a new insulation material extracted from date palm trees surface fibers, *Construction and Building Materials*. 2017;138:276–284. Available: <https://doi.org/10.1016/j.conbuildmat.2017.02.012>
- Ons Hamdaoui, Laurent Ibos, Atef Mazioud, Mohamed Safi, Oualid Limam. Thermophysical characterization of *Posidonia Oceanica* marine fibers intended to be used as an insulation material in Mediterranean buildings, *Construction and Building Materials*. 2018;180:68–76.

- Available:<https://doi.org/10.1016/j.conbuildmat.2018.05.195>
12. Kangcheng Wei, Chenglong Lv, Minzhi Chen, Xiaoyan Zhou, Zhenyu Dai, Da Shen, Development and performance evaluation of a new thermal insulation material from rice straw using high frequency hot-pressing, Energy and Buildings. 2015;87:116–122. Available:<https://doi.org/10.1016/j.enbuild.2014.11.026>
  13. Baley C, Le Duigou A, Bourmaud A, Davies P. Influence of drying on the mechanical behavior of flax fibers and their unidirectional composites. Compos. Appl. Sci. Manuf. 2012 ;43(8): 1226-1233. Available:<https://doi.org/10.1016/j.compositesa.2012.03.005>
  14. Fidelis AME, Pereira CTV, Gomes MOS, Sylva AF, Filho TRD. The effet of fiber morphology on the tensile strength of naturals fibers. J. Mater. Res. Technol. 2013;2(2):149-157. Available:<http://dx.doi.org/10.1016/j.jmrt.2013.02.003>
  15. Belaadi A, Amroune S, Bourchak M. Effect of eco-friendly chemical sodium bicarbonate treatment on the mechanical properties of flax fibers: Weibull statistics. International Journal of Advanced Manufacturing Technology. 2020;106: 1753–74. Available:<https://doi:10.1007/s00170-019-04628-8>
  16. Betené ADO, Betené EF, Ngali EFP, Noah PMA, Ndiwé B, Soppie AG, Atangana A, Moukené R. Influence of sampling area and extraction method on the thermal, physical and mechanical properties of Cameroonian Ananas comosus leaf fibers. Heliyon. 2022;8(8):e10127. Available:<https://doi.org/10.1016/j.heliyon.2022.e10127>
  17. Ghabo A, Toure PM, Dieye Y, Sambou V. Thermophysical characterization of concrete reinforced with baobab trunk fibers (*Adansonia digitata* L.) for thermal insulation of buildings. J Sustain Const Mater Technol. 2023;8(4):251–259. Available:<https://doi.org/10.47481/jscmt.1285031>
  18. Abderraouf Achour, Fouad Ghomari, Naima Belayachi. Properties of cementitious mortars reinforced with natural fibers, Journal of Adhesion Science and Technology; 2017. Available:[https://doi:10.1080/01694243.2017.1290572](https://doi.org/10.1080/01694243.2017.1290572)
  19. Bezazi A, Belaadi A, Bourchak M, Scarpa F, Boba K. Novel extraction techniques, chemical and mechanical characterisation of *Agave americana* L. natural fibers. Composites Part B: Engineering 2014;66: 194–203. Available:<https://doi:10.1016/j.compositesb.2014.05.014>
  20. Indira KN, Jyotishkumar P, Sabu T. Mechanical properties and failure topography of banana fiber PF macrocomposites fabricated by RTM and CM techniques. International Scholarly Research Notices 2013:936048. Available:<https://doi:10.1155/2013/936048>.
  21. Hamza S, Saad H, Charrier B, Ayed N, Bouhtoury FCE. Physico-chemical characterization of Tunisian plant fibers and its utilization as reinforcement for plaster-based composites. Ind. Crpo. Prod. 2013;49:357-365. Available:<https://doi.org/10.1016/j.indcrop.2013.04.052>
  22. Budsaraporn S, Paweena T, Taweechai A. Revisiting the morphology, microstructure and properties of cellulose fibers from pineapple leaf so as to expand its utilization. Sains Malays. 2019;48(1):145-154. Available:<http://dx.doi.org/10.17576/jsm-2019-4801-17>
  23. Sikamé TNR, Njeugna E, Fogue M, Drean J -Y, Nzeukou A, Fokwa D. 2014. Study of water absorption in raffia vinifera fibers from Bandjoun, Cameroon. Scientific World Journal. 2014:912320. Available:<https://doi:10.1155/2014/912380>.
  24. Saikia D. Studies of water absorption behavior of plant fibers at different temperatures. International Journal of Thermophysics. 2010;31(4-5):1020-1026. Available:<https://doi :10.1007/s10765-010-0774-0>.
  25. Camille Magniont, Contribution à la Formulation et à la Caractérisation d'un éco Matériau de Construction à Base d'Agro Ressources, Université Toulouse III - Paul Sabatier; 2010.
  26. Manivel S, Pannirselvam N, Gopinath R, Sathishkumar TP. Physico-mechanical, chemical composition and thermal properties of cellulose fiber from hibiscus vitifolius plant stalk for polymer composites. Journal of Natural Fibers. 2021;19(13):6961–76.



- Available:<https://doi:10.1080/15440478.2021.1941484>.
27. John MJ, Anandjiwala RD. Recent developments in chemical modification and characterization of natural fiber-reinforced composites. *Polymer Composites*. 2008; 29(2):187–207. Available:<https://doi:10.1002/pc.20461>.

© Copyright (2024): Author(s). The licensee is the journal publisher. This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

*Peer-review history:*

*The peer review history for this paper can be accessed here:*

*<https://www.sdiarticle5.com/review-history/114789>*